

TECHNICAL SPECIFICATION



Photovoltaic cells –
Part 3: Measurement of current-voltage characteristics of bifacial photovoltaic
cells

IECNORM.COM : Click to view the full PDF of IEC TS 63202-3:2023



THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2023 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 300 terminological entries in English and French, with equivalent terms in 19 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IECNORM.COM : Click to view the full PDF of IEC 60320-23:2023

TECHNICAL SPECIFICATION



**Photovoltaic cells –
Part 3: Measurement of current-voltage characteristics of bifacial photovoltaic
cells**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 27.160

ISBN 978-2-8322-6415-7

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	3
1 Scope.....	5
2 Normative references	5
3 Terms and definitions	6
4 Methods	7
4.1 General.....	7
4.2 Double-side simultaneous irradiation	8
4.3 Equivalent irradiation	8
4.4 Sequential irradiation	10
5 Apparatus.....	11
5.1 General.....	11
5.2 Double-side simultaneous irradiation	11
5.3 Equivalent irradiation	11
5.4 Sequential irradiation	12
6 Procedures.....	12
6.1 General.....	12
6.2 Double-side simultaneous irradiation	12
6.2.1 Requirements for calibration	12
6.2.2 Procedures	13
6.3 Equivalent irradiation	13
6.3.1 Requirements for calibration	13
6.3.2 Procedures	13
6.4 Sequential irradiation	14
6.4.1 Requirements for calibration	14
6.4.2 Procedures	14
7 Report	15
Annex A (normative) Determination of bifacial I-V characteristics.....	16
A.1 General.....	16
A.2 Shift approximation	16
A.3 Linear interpolation	17
Figure 1 – Schematic procedure of double-side simultaneous irradiation method with integrated flash conditions	8
Figure 2 – Schematic procedure of equivalent irradiation method with sequential flash conditions	9
Figure 3 – Schematic procedure of equivalent irradiation method with integrated flash conditions	10
Figure 4 – Schematic procedure of sequential irradiation method with integrated flash conditions	10
Figure 5 – Separate solar simulator on both front and rear side for double-side simultaneous irradiation	11
Figure 6 – Setup for equivalent irradiation with adjustable intensity	12
Figure 7 – Schematic configuration with two consecutive solar simulators	12

INTERNATIONAL ELECTROTECHNICAL COMMISSION

PHOTOVOLTAIC CELLS –

Part 3: Measurement of current-voltage characteristics of bifacial photovoltaic cells

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

IEC TS 63202-3 has been prepared by IEC technical committee 82: Solar photovoltaic energy systems. It is a Technical Specification.

The text of this Technical Specification is based on the following documents:

Draft	Report on voting
82/2070/DTS	82/2094/RVDTS
	82/2094A/RVDTS

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this Technical Specification is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at https://www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at <https://www.iec.ch/standardsdev/publications>.

A list of all parts in the IEC 63202 series, published under the general title *Photovoltaic cells*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

IECNORM.COM : Click to view the full PDF of IEC TS 63202-3:2023

PHOTOVOLTAIC CELLS –

Part 3: Measurement of current-voltage characteristics of bifacial photovoltaic cells

1 Scope

This part of IEC 63202 describes procedures for the measurement of current-voltage (I-V) characteristics of crystalline silicon bifacial photovoltaic (PV) cells for both laboratory and mass production applications.

This document is intended to be used for measurement of individual unencapsulated bifacial PV cells, in addition to the requirements described in IEC 60904-1 and differentiating from IEC TS 60904-1-2 which is more applicable to encapsulated PV device. Specific requirements on bifacial reference cells and calibration of solar simulators are also defined to provide useful guidance for the proposed methods.

The bifacial I-V characteristics contain front standard test condition (STC), rear STC and bifacial STC results for the bifacial PV cells under test. Thus, bifaciality as well as the power generation capability under single-side or bifacial irradiation are evaluated.

NOTE This document does not apply to tandem or multi-junction bifacial PV cells.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60891, *Photovoltaic devices – Procedures for temperature and irradiance corrections to measured I-V characteristics*

IEC 60904-1, *Photovoltaic devices – Part 1: Measurement of photovoltaic current-voltage characteristics*

IEC TS 60904-1-2, *Photovoltaic devices – Part 1-2: Measurement of current-voltage characteristics of bifacial photovoltaic (PV) devices*

IEC 60904-2, *Photovoltaic devices – Part 2: Requirements for photovoltaic reference devices*

IEC 60904-4, *Photovoltaic devices – Part 4: Photovoltaic reference devices – Procedures for establishing calibration traceability*

IEC 60904-7, *Photovoltaic devices – Part 7: Computation of the spectral mismatch correction for measurements of photovoltaic devices*

IEC 60904-9, *Photovoltaic devices – Part 9: Classification of solar simulator characteristics*

IEC 61215-1:2021, *Terrestrial photovoltaic (PV) modules – Design qualification and type approval – Part 1: Test requirements*

IEC TS 61836, *Solar photovoltaic energy systems – Terms, definitions and symbols*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC TS 61836 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

bifacial standard test condition

BSTC

testing conditions that simultaneously meet the following requirements: spectral irradiance distribution according to AM1.5 on both sides, cell temperature of 25 °C, front irradiation intensity of 1 000 W · m⁻², and rear irradiation intensity of 135 W · m⁻²

3.2

low reflection background

testing environment using anti-reflective materials and/or design to reduce the influence of ambient light or light reflected from the testing environment on the intentional irradiance applied to the bifacial PV cells under test

Note 1 to entry: The background is considered to be low reflection, if the difference in short-circuit current is less than 0,3 % when the bifacial PV cell is irradiated single-sided under STC condition, and the non-irradiated side is covered or non-covered.

3.3

bifaciality

ratio between rear and front I-V characteristics of bifacial PV cells

Note 1 to entry: By default, rear STC and front STC I-V characteristics are used to determine bifaciality.

Note 2 to entry: Main bifaciality coefficients include short-circuit current bifaciality φ_{isc} , open-circuit voltage bifaciality φ_{voc} and maximum power bifaciality φ_{Pmax} .

Note 3 to entry: The definition of bifaciality is consistent with IEC TS 60904-1-2.

Note 4 to entry: The subscripts “f” and “r” stand for values derived from front- and rear-side measurements, respectively.

3.4

bifacial reference cell

reference cell with bifacial structure similar to the bifacial PV cells under test

Note 1 to entry: The I-V characteristics of the bifacial reference cell, typically calibrated by certified calibration laboratories, are used to calibrate the irradiance of solar simulators. Detailed requirements of bifacial reference cell depend on the method to measure the bifacial PV cells under test.

3.5

bifacial I-V characteristics

I-V characteristics of bifacial PV cells under bifacial standard testing condition (BSTC) with contributions from both front-side and rear-side irradiation

Note 1 to entry: Main bifacial I-V characteristics include bifacial short-circuit current $I_{sc_{BIFI}}$, bifacial open-circuit voltage $V_{oc_{BIFI}}$ and bifacial maximum power $P_{max_{BIFI}}$.

Note 2 to entry: Bifacial I-V characteristics are obtained from direct measurement or equivalent calculation and can be used to evaluate the power generation capability of bifacial PV cells under double-side irradiation.

3.6 bifacial power gain coefficient

$BiFi_{rel}$

gain of $P_{max_{BiFi}}$ with respect to P_{max_f} as $BiFi_{rel} = \left(\frac{P_{max_{BiFi}}}{P_{max_f}} - 1 \right) \times 100 \%$

4 Methods

4.1 General

In most cases, bifacial PV modules are operated under double-side irradiance in the outdoor environment. The additional energy yield gain of bifacial PV modules compared to monofacial PV modules comes from the irradiance on the rear-side of the bifacial PV modules.

To evaluate the power generation capability of bifacial PV cells, the I-V characteristics shall be reported at bifacial nameplate irradiance (BNPI), as defined in 3.11 of IEC 61215-1:2021. It corresponds to a front-side irradiance, $G_f = 1\,000\text{ W} \cdot \text{m}^{-2}$, and a rear-side irradiance, $G_r = 135\text{ W} \cdot \text{m}^{-2}$, on the device under test. Deviation of the measurement test conditions from the reporting standard test conditions are allowed (temperature and irradiance), in which case correction according to IEC 60891 shall be applied and taken into account in the uncertainty calculations.

One out of the following three methods shall be used for measuring bifacial PV cells, depending on the apparatus available. The three methods yield equivalent results following the procedures and requirements described in this document.

- a) Double-side simultaneous irradiation.
- b) Equivalent irradiation.
- c) Sequential irradiation.

The double-side simultaneous irradiation method requires a specific apparatus to provide irradiance to both sides of the bifacial PV cells under test. The monofacial and bifacial I-V characteristics of each cell under test can be measured at the same position and with a single contacting unit and cycle.

Alternatively, the equivalent irradiation method can be used with conventional apparatus for measuring monofacial PV cells. The equivalent irradiation intensity, G_E , is determined in formula (1) using the bifaciality, φ_{IsC} , as follows:

$$G_E = 1\,000 + \varphi_{IsC} \times 135\text{ W} \cdot \text{m}^{-2} \quad (1)$$

When measurement time allows (typically for laboratory applications), φ_{IsC} is determined by measuring front STC and rear STC I-V characteristics of each cell under test. When measurement time is limited (typically for mass production applications), φ_{IsC} can be inferred from a bifacial reference cell and reported as representative to all cells under test. The error resulting from such a method is acceptable if the production spread of φ_{IsC} remains within $\pm 3\%$ relative to that of the bifacial reference cell. Sampling of the spread of φ_{IsC} shall be taken into consideration for mass production applications.

The sequential irradiation method can also be used with conventional apparatus. The front-side and rear-side of the bifacial PV cells are characterised in sequence, requiring the cells to be flipped between measurements. The measured front STC, rear STC and optional rear low irradiance I-V characteristics are used to calculate the bifacial I-V characteristics following procedures described in the Annexes to this document based on IEC 60891.

4.2 Double-side simultaneous irradiation

With the bifacial PV cells under test placed in a low reflection background environment, the front STC, rear STC and bifacial I-V characteristics are respectively measured by applying front STC only, rear STC only and simultaneously BSTC irradiation to the bifacial PV cells.

For laboratory application, the front STC, rear STC and BSTC irradiations to the bifacial PV cell under test can be conducted separately and in any sequence.

For mass production application where cycle time matters, the three measurement steps are typically integrated into one sequence. An example schematic procedure of double-side simultaneous irradiation method with integrated flash conditions is shown in Figure 1.

- a) step 1 (t1-t2): measure rear STC I-V characteristics under rear STC irradiation;
- b) step 2 (t3-t4): measure bifacial I-V characteristics under BSTC irradiation;
- c) step 3 (t5-t6): measure front STC I-V characteristics under front STC irradiation.

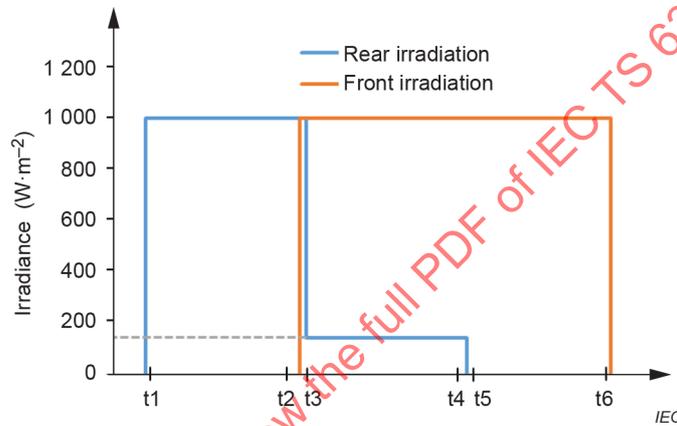


Figure 1 – Schematic procedure of double-side simultaneous irradiation method with integrated flash conditions

In this case, since double-side simultaneous irradiation is used, the irradiance correction described in IEC 60891 cannot be applied without adaptation. The required adaptation is described in formulae (2) and (3) by calculating the equivalent measured, $G_{E,meas}$, and BSTC, $G_{E,BSTC}$, irradiance, such that:

$$G_{E,meas} = G_f + \varphi_{Isc} \times G_r \text{ W} \cdot \text{m}^{-2} \tag{2}$$

$$G_{E,BSTC} = 1\,000 + \varphi_{Isc} \times 135 \text{ W} \cdot \text{m}^{-2} \tag{3}$$

Then $G_1 = G_{E,meas}$ and $G_2 = G_{E,BSTC}$ can be applied in procedure 1 or 2 of IEC 60891. As in IEC 60904-1, deviation up to 10 % from STC or BSTC conditions are acceptable. For BSTC however, irradiance of the rear-side light source should not be smaller than $100 \text{ W} \cdot \text{m}^{-2}$ in order to achieve sufficient contribution from the rear side.

4.3 Equivalent irradiation

With the bifacial PV cells under test placed in a low reflection background environment, the front STC, rear STC and equivalent bifacial I-V characteristics are respectively measured by applying front STC, rear STC and front-side equivalent irradiation to the bifacial PV cells. Depending on the set-up and limitation of measurement time, equivalent irradiation method can be conducted in different approaches.

One approach is to sequentially measure front STC, rear STC and equivalent bifacial I-V characteristics of cell under test. For the latter, the φ_{ISC} of each cell under test is used to determine the equivalent irradiation intensity G_E .

The sequential irradiation process can be conducted with one solar simulator, typically for laboratory application, or under the irradiation of two consecutive solar simulators, typically in a production line.

An example schematic procedure of such approach is shown in Figure 2.

- a) step 1 (t1-t2): measure front STC I-V characteristics under front STC irradiation;
- b) step 2 (t3-t4): measure rear STC I-V characteristics under rear STC irradiation;
- c) step 3 (t5-t6): measure equivalent bifacial I-V characteristics under equivalent irradiation.

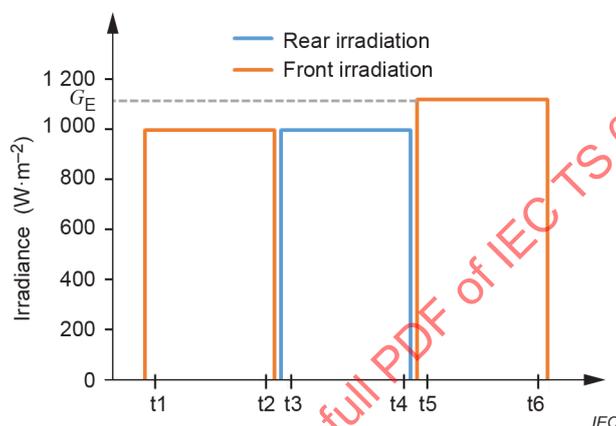


Figure 2 – Schematic procedure of equivalent irradiation method with sequential flash conditions

Another approach is to measure front STC and equivalent bifacial I-V characteristics of cell under test, usually under one contacting and one integrated flash condition. φ_{ISC} , inferred from a bifacial reference cell and assumed to be representative for all cells under test, is used to determine the equivalent irradiation intensity G_E . The error resulting from such approach is acceptable if the spread of φ_{ISC} of cells under test remains within $\pm 3\%$ relative to that of the bifacial reference cell.

An example schematic procedure of this approach is shown in Figure 3.

- a) step 1 (t1-t2): measure equivalent bifacial I-V characteristics under equivalent irradiation;
- b) step 2 (t3-t4): measure front STC I-V characteristics under front STC irradiation.

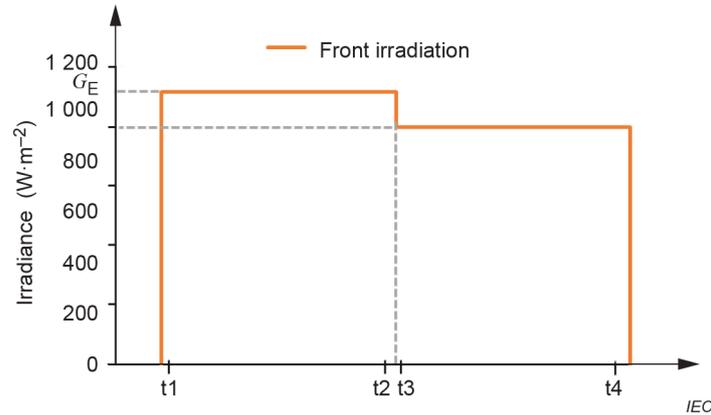


Figure 3 – Schematic procedure of equivalent irradiation method with integrated flash conditions

4.4 Sequential irradiation

With the bifacial PV cells under test placed in a low reflection background environment, the front STC, rear STC, and optional rear $135 \text{ W} \cdot \text{m}^{-2}$ I-V characteristics are measured by applying front STC, rear STC, and optional rear $135 \text{ W} \cdot \text{m}^{-2}$ irradiance to the bifacial PV cells, respectively. The bifacial I-V characteristics are then determined by theoretical modelling which is described in Annex A based on IEC 60891.

The sequential irradiation process can be conducted with one solar simulator, typically for laboratory application, or under the irradiation of two consecutive solar simulators, typically in a production line.

A schematic procedure of the sequential irradiation method is shown in Figure 4.

- a) step 1 (t1-t2): measure front STC I-V characteristics under front STC irradiation;
- b) step 2 (t3-t4): measure rear STC I-V characteristics under rear STC irradiation;
- c) step 3 (t5-t6, optional): measure rear I-V characteristics under rear $135 \text{ W} \cdot \text{m}^{-2}$ irradiation;
- d) step 4: calculate the bifacial I-V characteristics using the procedures for irradiance correction of measured I-V characteristics described in Annex A based on IEC 60891.

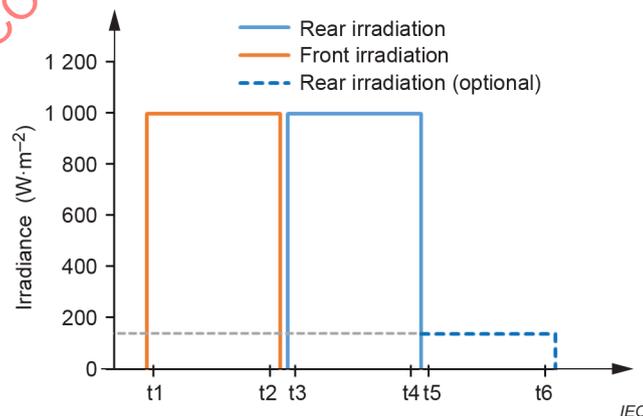


Figure 4 – Schematic procedure of sequential irradiation method with integrated flash conditions

5 Apparatus

5.1 General

In addition to the requirements described in IEC 60904-1 and IEC 60904-9, the requirements of solar simulator systems for measuring bifacial PV cells are described in this document.

When the solar simulator's irradiation extends over the designated cell area and beyond the measurement plane, it is highly recommended to employ features such as baffles in the measurement setup. Further, equipment enabling a monitored and controlled temperature environment should be used to maintain temperatures in accordance with STC and BSTC.

5.2 Double-side simultaneous irradiation

A solar simulator system for double-side simultaneous irradiation is specified to meet the requirements as defined in IEC 60904-9, as well as following the additional requirements:

- Be able to irradiate simultaneously both sides of the bifacial PV cells and separately each side of the bifacial PV cells.
- Front irradiation shall be able to provide irradiance levels up to $1\,135\text{ W}\cdot\text{m}^{-2}$, and rear irradiation shall be able to provide adjustable irradiance level from $100\text{ W}\cdot\text{m}^{-2}$ to $1\,000\text{ W}\cdot\text{m}^{-2}$.
- Low reflection background and aperture masks should be provided to ensure, that the non-irradiated surface of the cell receives less than $3\text{ W}\cdot\text{m}^{-2}$ of light from the light source when irradiating the other side of the cell.

An example of a solar simulator system for double-side simultaneous irradiation is shown in Figure 5.

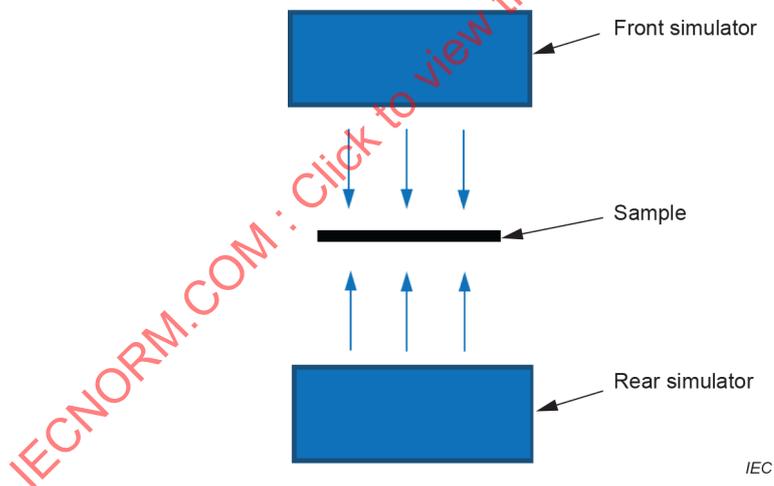


Figure 5 – Separate solar simulator on both front and rear side for double-side simultaneous irradiation

5.3 Equivalent irradiation

A solar simulator system for equivalent irradiation is specified to meet the requirements as defined in IEC 60904-9, as well as following the additional requirements:

- Front irradiation shall be able to provide irradiance levels up to $1\,135\text{ W}\cdot\text{m}^{-2}$.
- Low reflection background and/or aperture masks should be placed during I-V measurement to ensure, the non-irradiated rear-side of the cell under test receives less than $3\text{ W}\cdot\text{m}^{-2}$ of light from the light source.

An example of a solar simulator system for equivalent irradiation is shown in Figure 6.

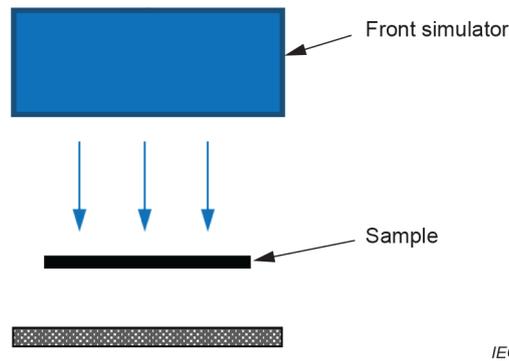


Figure 6 – Setup for equivalent irradiation with adjustable intensity

5.4 Sequential irradiation

A solar simulator system for sequential irradiation is specified to meet the requirements as defined in IEC 60904-9, as well as following the additional requirements:

- a) Low reflection background and/or aperture masks should be placed during I-V measurement to ensure, the non-irradiated rear-side of the cell under test receives less than $3 \text{ W} \cdot \text{m}^{-2}$ of light from the light source.

An example configuration with two consecutive solar simulators for sequential irradiation is shown in Figure 7.

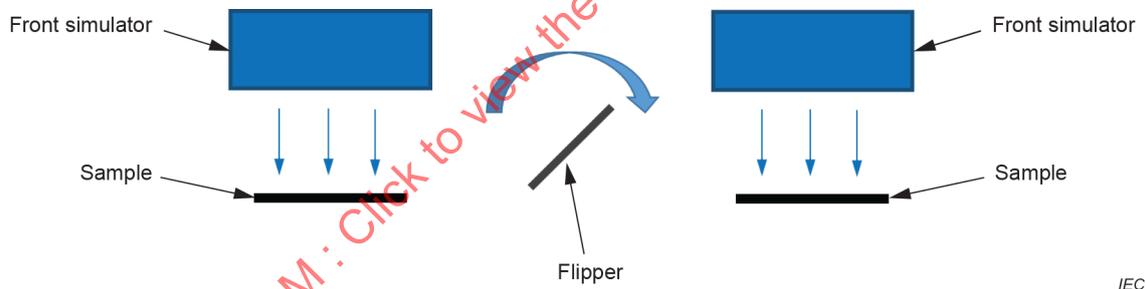


Figure 7 – Schematic configuration with two consecutive solar simulators

6 Procedures

6.1 General

For measurements of I-V characteristics of bifacial PV cells, the procedures should firstly be specified to meet the requirements as defined in IEC 60904-1, IEC 60904-2, IEC 60904-4, IEC 60904-9 and IEC 60891.

6.2 Double-side simultaneous irradiation

6.2.1 Requirements for calibration

Typically, the spectral response of a bifacial PV cell differs between its front-side and rear-side. Caution should be taken when calibrating the front and rear solar simulators, for example by using a representative bifacial reference cell.

For the bifacial reference cell calibrated by an external calibration laboratory, at least three sets of calibrated I-V characteristics are required, namely, that measured at front STC, rear STC and rear $135 \text{ W} \cdot \text{m}^{-2}$.

For both front-side and rear-side measurement under STC irradiation, the spectral mismatch between the bifacial reference cell and bifacial PV cells under test should not exceed 0,5 %. Otherwise, a spectral mismatch correction according to IEC 60904-7 is required.

6.2.2 Procedures

Step 1: Calibrate the solar simulator for front STC measurement at $1\,000 \text{ W} \cdot \text{m}^{-2}$, using front STC I-V characteristics of the bifacial reference cell.

Step 2: Calibrate the solar simulator for rear measurement at $1\,000 \text{ W} \cdot \text{m}^{-2}$ and $135 \text{ W} \cdot \text{m}^{-2}$, using rear STC and rear $135 \text{ W} \cdot \text{m}^{-2}$ I-V characteristics of the bifacial reference cell.

Step 3: Under front STC irradiation, measure the front STC I-V characteristics (P_{max_f} , I_{sc_f} , V_{oc_f}) of the bifacial PV cell under test.

Step 4: Under rear STC irradiation, measure the rear STC I-V characteristics (P_{max_r} , I_{sc_r} , V_{oc_r}) of the bifacial PV cell under test.

Step 5: Under BSTC irradiation, measure the bifacial I-V characteristics ($P_{max_{BiFi}}$, $I_{sc_{BiFi}}$, $V_{oc_{BiFi}}$) of the bifacial PV cell under test.

Step 6: Calculate the bifacial power gain coefficient $BiFi_{rel}$ as defined in 3.6.

For various setups of the solar simulator systems, Step 1 and Step 2 can be conducted in any sequence, and Step 3 through Step 5 can be conducted in any sequence.

6.3 Equivalent irradiation

6.3.1 Requirements for calibration

Typically, the spectral response of a bifacial PV cell differs between its front-side and rear-side. Therefore, it is necessary to calibrate the solar simulator for front and rear side measurement separately, using a suitable bifacial reference cell.

For the bifacial reference cell calibrated by an external calibration laboratory, at least two sets of calibrated I-V characteristics are required, namely, that measured at front STC and rear STC. A third measurement at front equivalent irradiation intensity G_E is recommended.

For all three conditions, front STC, rear STC and equivalent irradiation, the spectral mismatch between the bifacial reference cell and bifacial PV cells under test should not exceed 0,5 %. Otherwise, a spectral mismatch correction according to IEC 60904-7 is required.

6.3.2 Procedures

Step 1: Calibrate the solar simulator for front STC measurement at $1\,000 \text{ W} \cdot \text{m}^{-2}$, using front $1\,000 \text{ W} \cdot \text{m}^{-2}$ I-V characteristics of the bifacial reference cell.

Step 2: Calibrate the solar simulator for front measurement at G_E , using front equivalent irradiation I-V characteristics of the bifacial reference cell.

Step 3: Calibrate the solar simulator for rear STC measurement at $1\,000\text{ W}\cdot\text{m}^{-2}$, using rear STC I-V characteristics of the bifacial reference cell. The $1\,000\text{ W}\cdot\text{m}^{-2}$ setpoint for rear side irradiation may differ from the $1\,000\text{ W}\cdot\text{m}^{-2}$ front irradiation due to the differences in spectral response between front and rear side of the bifacial reference cell.

Step 4: Under front STC irradiation, measure the front STC I-V characteristics (P_{max_f} , I_{sc_f} , V_{oc_f}) of the bifacial PV cell under test.

Step 5: Under rear STC irradiation, measure the rear STC I-V characteristics (P_{max_r} , I_{sc_r} , V_{oc_r}) of the bifacial PV cell under test.

Step 6: Use the front STC and rear STC I-V characteristics measured in Step 4 and Step 5 to determine φ_{ISC} and G_E . Alternatively, G_E of the bifacial reference cell may be used if the cell is not characterized with rear irradiation.

Step 7: Under equivalent irradiation intensity G_E , measure the equivalent bifacial I-V characteristics ($P_{max_{BiFi}}$, $I_{sc_{BiFi}}$, $V_{oc_{BiFi}}$) of the bifacial PV cell under test.

Step 8: Calculate the bifacial power gain coefficient $BiFi_{rel}$ as defined in 3.6.

For various setups of the solar simulator systems, Step 1 through Step 3 can be conducted in any sequence, and Step 4 and Step 5 can be conducted in any sequence.

6.4 Sequential irradiation

6.4.1 Requirements for calibration

Typically, the spectral response of a bifacial PV cells differs between its front-side and rear-side. Therefore, it is recommended to calibrate the front and rear solar simulators separately, using a suitable bifacial reference cell. In the case where one simulator system is used for both measurements, different calibrations for front and rear side measurements are still recommended. If not, spectral mismatch corrections according to IEC 60904-7 should be performed and reported.

For the bifacial reference cell calibrated by an external calibration laboratory, at least two sets of calibrated I-V characteristics are required, namely, that measured at front STC and rear STC. When the rear $135\text{ W}\cdot\text{m}^{-2}$ I-V characteristics is also measured for the bifacial PV cell under test, additional calibrated I-V characteristics of rear $135\text{ W}\cdot\text{m}^{-2}$ are required of the bifacial reference cell.

For both front-side and rear-side measurement under STC irradiation, the spectral mismatch between the bifacial reference cell and bifacial PV cells under test should not exceed 0,5 %. Otherwise, a spectral mismatch correction according to IEC 60904-7 is required.

6.4.2 Procedures

Step 1: Calibrate the solar simulator for front STC measurement at $1\,000\text{ W}\cdot\text{m}^{-2}$, using the front STC I-V characteristics of the bifacial reference cell.

Step 2: Calibrate the solar simulator for rear measurement at $1\,000\text{ W}\cdot\text{m}^{-2}$, and optionally at $135\text{ W}\cdot\text{m}^{-2}$, using the rear I-V characteristics of the bifacial reference cell.

Step 3: Under front STC irradiation, measure the front STC I-V characteristics (P_{max_f} , I_{sc_f} , V_{oc_f}) of the bifacial PV cells under test.

Step 4: Under rear STC irradiation, and optionally at $135\text{ W}\cdot\text{m}^{-2}$, measure the rear I-V characteristics (P_{max_r} , I_{sc_r} , V_{oc_r}) of the bifacial PV cells under test.

Step 5: Derive the bifacial I-V curve using the procedures described in the Annexes, then calculate the bifacial I-V characteristics ($P_{max_{BiFi}}$, $I_{SC_{BiFi}}$, $V_{OC_{BiFi}}$).

Step 6: Calculate the bifacial power gain coefficient $BiFi_{rel}$ as defined in 3.6.

For various setups of the solar simulator systems, Step 1 and Step 2 can be conducted in any sequence, and Step 3 and Step 4 can be conducted in any sequence.

7 Report

For bifacial PV devices, following completion of the procedure, a report of the I-V measurements shall be prepared. The test report shall include the information as required by IEC 60904-1, IEC 60904-2 and IEC 60904-4, and additionally the following shall be included together with their uncertainty estimate:

- Information of calibration, i.e. name of external calibration laboratory for reference cell, method used to calibrate solar simulators, traceability of calibration.
- Bifaciality coefficient φ_{ISC} , φ_{Voc} and φ_{Pmax} .
- Bifacial I-V characteristics $P_{max_{BiFi}}$, $I_{SC_{BiFi}}$, $V_{OC_{BiFi}}$, and the method used to measure bifacial I-V characteristics.
- Bifacial power gain coefficient $BiFi_{rel}$.

IECNORM.COM : Click to view the full PDF of IEC TS 63202-3:2023