
**Footwear — Test methods for
accessories: Touch and close
fasteners — Shear strength before and
after repeated closing**

*Chaussures — Méthodes d'essai pour accessoires: fermetures
auto-agrippantes — Résistance à la traction avant et après un usage
répété*



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 22776:2004

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 22776 was prepared by the European Committee for Standardization (CEN) in collaboration with Technical Committee ISO/TC 216, *Footwear*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this document, read “...this European Standard...” to mean “...this International Standard...”.

Annex ZA provides a list of corresponding International and European Standards for which equivalents are not given in the text.

Contents

| | Page |
|--|------|
| Foreword..... | v |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 1 |
| 4 Principle | 1 |
| 4.1 Shear strength..... | 1 |
| 4.2 Shear strength after repeated opening and closing | 1 |
| 5 Apparatus | 2 |
| 6 Test specimens | 5 |
| 7 Conditioning..... | 5 |
| 8 Procedure | 6 |
| 9 Calculation and expression of results..... | 8 |
| 10 Test report | 8 |
| Annex ZA (normative) Normative references to International publications with their corresponding European publications..... | 9 |

Foreword

This document (EN ISO 22776:2004) has been prepared by Technical Committee CEN/TC 309 "Footwear", the secretariat of which is held by AENOR, in collaboration with Technical Committee ISO/TC 216 "Footwear".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2005, and conflicting national standards shall be withdrawn at the latest by June 2005.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

1 Scope

This document specifies a test method for determining the longitudinal shear strength of touch and close fasteners before and after repeated use.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 12222, *Footwear - Standard atmospheres for conditioning and testing of footwear and components for footwear*

EN 12240, *Touch and close fasteners — Determination of the overall and effective widths of tapes and the effective width of a closure*

EN ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system (ISO 7500-1:2004)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

longitudinal shear strength

maximum force per unit effective area required to separate the two tapes forming the specified closure in a shearing action under the specified conditions of test

3.2

effective width

width of the pile at 90° to the length of the tape and which does not include the selvedge

3.3

effective area of a closure

product of the effective width of a closure and the length of a closure

4 Principle

4.1 Shear strength

Mated component tapes of a touch and close fastener are separated at a constant rate along the closure in a direction parallel to the length of the tapes forming the closure and in the plane of the closure.

4.2 Shear strength after repeated opening and closing

A touch and close fastener is repeatedly opened and closed a standard number of times by a machine. The shear strength is then measured by repeating the test described in 4.1.

5 Apparatus

5.1 A **tensile testing machine** complying with the requirements of EN ISO 7500-1 to an accuracy corresponding to class 2, and with the following:

5.1.1 A jaw separation rate of 100 mm/min \pm 10 mm/min.

5.1.2 The means of producing a continuous record of force throughout the test.

5.2 A **roller device** with a roller (see Figure 1) of diameter 100 mm \pm 5 mm capable of applying a force of 1,0 N \pm 0,1 N per millimetre width of the test specimen. This is to close the fastener under a standard pressure.

5.3 **Fork** with a handle (see Figure 2) which engages the roller (5.2) and allows it to be moved without any extra down force being applied (see Figure 3).


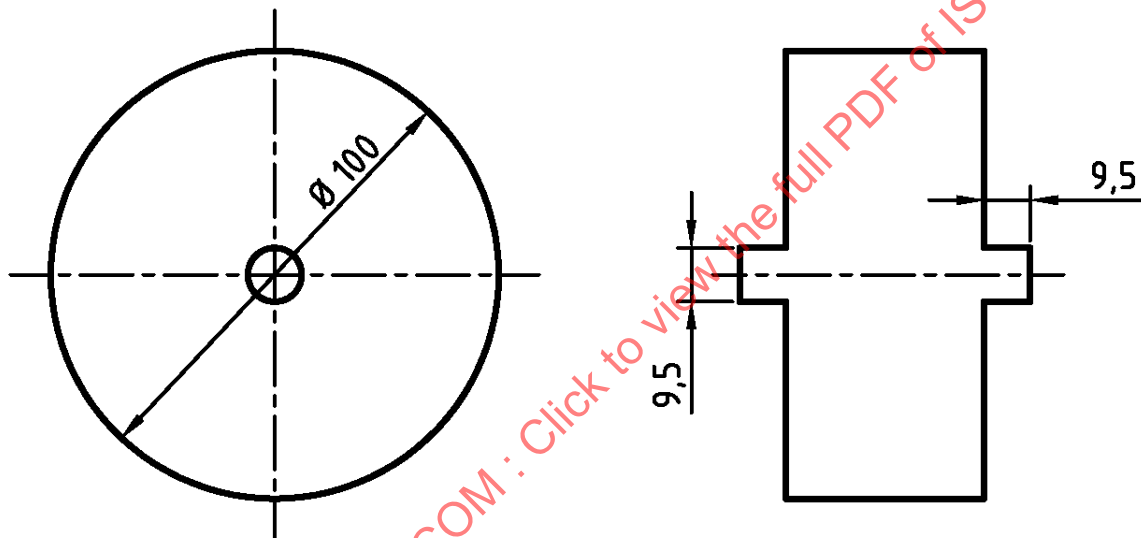


Figure 1 — Roller

Dimensions in mm

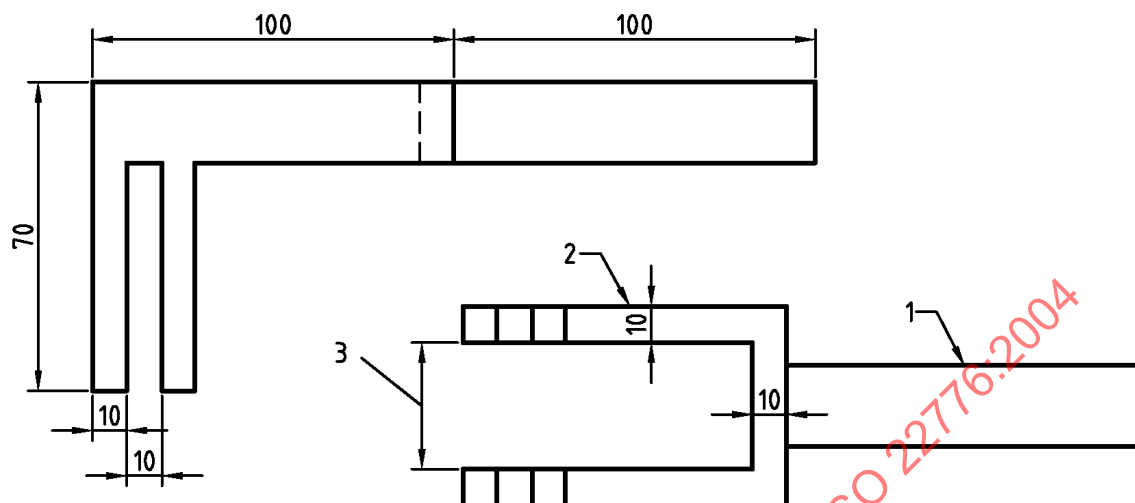

Key

- 1 Handle
- 2 Forks
- 3 Space between the forks to be 2 mm greater than the roller width

Figure 2 — Fork with a handle

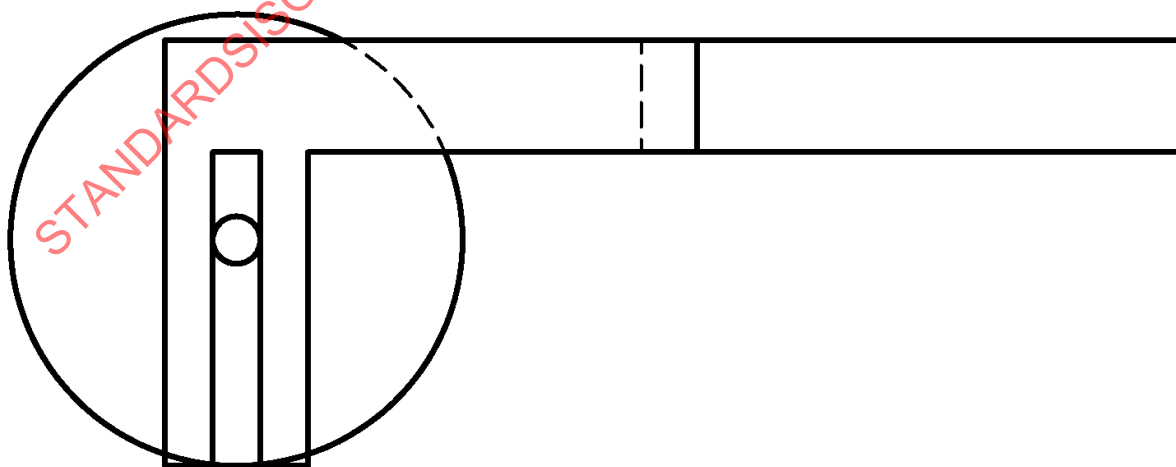


Figure 3 — Rolling mechanism for touch and close fasteners


5.4 A touch and close cycling machine (see Figure 4) with:

5.4.1 Two circular drums of minimum width 70 mm, one of diameter $160,0 \text{ mm} \pm 0,5 \text{ mm}$ and the other diameter $162,5 \text{ mm} \pm 0,5 \text{ mm}$. Each drum has a single slot of length $55 \text{ mm} \pm 2 \text{ mm}$ across its width to hold the free ends of the specimen fastener. The drums are mounted next to each other with their axes parallel.

5.4.2 A means of rotating the smaller of the two drums at a rate of $60 \text{ rev/min} \pm 5 \text{ rev/min}$ with the direction of rotation being reversed every $30 \text{ s} \pm 5 \text{ s}$. The larger of the two drums rotates freely and is driven by physical contact with the smaller drum via the test specimen.

5.4.3 A means of applying a force of $1,0 \text{ N} \pm 0,1 \text{ N}$ between the two drums for every 1 mm width of the test specimen.

5.4.4 A method of counting the total number of rotations of the smaller of the two drums regardless of the direction of rotation.

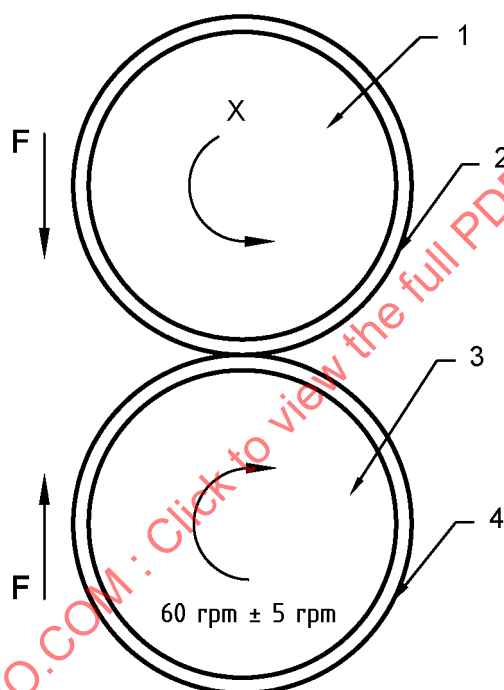

Key

- 1 Idling drum (diameter $162,5 \text{ mm} \pm 0,5 \text{ mm}$)
- 2 Hook tape
- 3 Driven drum (diameter $160 \text{ mm} \pm 0,5 \text{ mm}$)
- 4 Loop tape
- F Force between drums = $1 \text{ N} \times$ for every millimetre of effective width of fastener
- X Drum

Figure 4 — Touch and close fastener cycling machine

6 Test specimens

6.1 Shear strength


Cut four test specimens of both hook and loop components at least 100 mm long and mark each with a “1” at one end and a “2” at the other end (see Figure 5).

6.2 Shear strength after repeated opening and closing

6.2.1 Cut one piece of length $540 \text{ mm} \pm 10 \text{ mm}$ from both the hook and loop tapes.

6.2.2 Mark four test specimens, each of length $100 \text{ mm} \pm 5 \text{ mm}$ on the central portion of both tapes.

6.2.3 Mark each 100 mm test specimen section with a “1” at one end and a “2” at the other (see Figure 5). Do not cut the test specimens out at this stage.

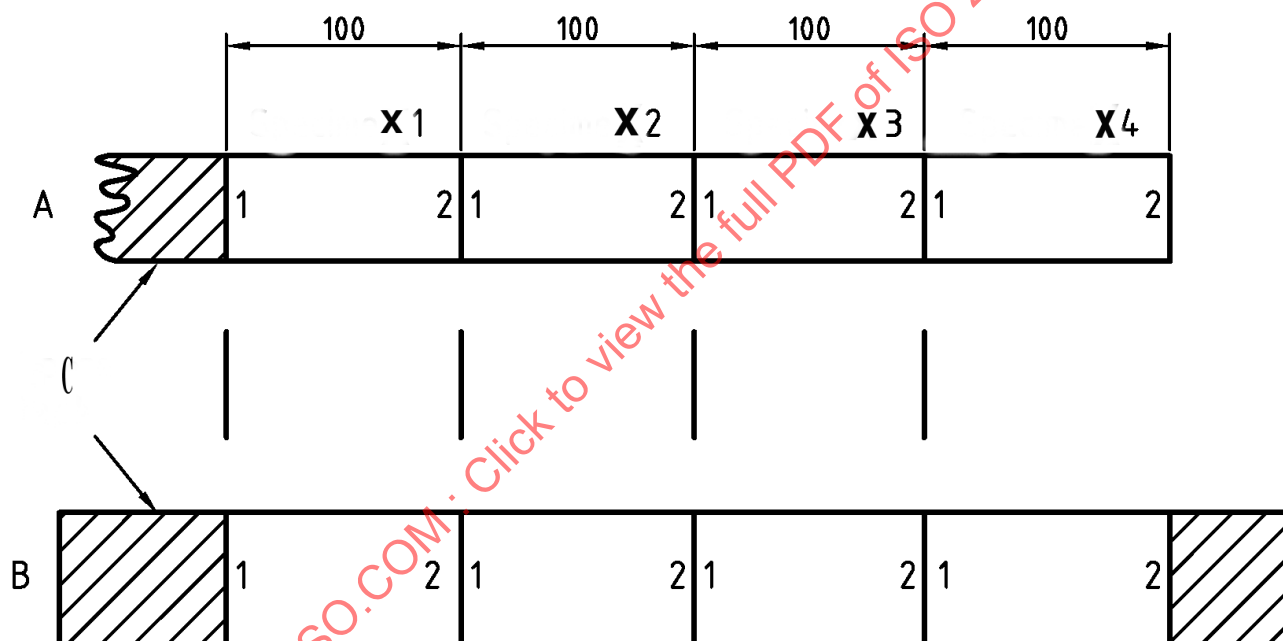

Key

- A Hook tape
- B Loop tape
- C Spare tape
- X Specimen

Figure 5 — Marking and cutting of test specimens

7 Conditioning

The test specimens shall be conditioned in accordance with the standard atmosphere specified in EN 12222 for a minimum of 24 h prior to the test. The closing of the test specimens and the testing shall also take place under these conditions.

8 Procedure

8.1 Shear strength

8.1.1 Measure the effective width (3.2), W_e , of both a hook and loop tapes (see 6.1), according to EN 12240, to an accuracy of 0,5 mm and use the smaller of these two values as the width of all the assembled fasteners.

8.1.2 Assemble (in accordance with the combinations of closure shown in Figure 6) the test specimens (see 6.1) as follows:

8.1.2.1 Select the length of overlap, L_o , in accordance with the following:

- 50 mm for fastener systems (see Figure 6) comprised of woven hook tape and woven loop tape;
- 20 mm for fastener systems comprised of either woven or knitted mushroom tape and knitted loop tape;
- 20 mm for fastener systems comprised of a plastic hook tape and knitted loop tape;
- 50 mm for fastener systems not listed here above, but in the event that tensile failure occurs to either of the tapes during testing, the overlap should be reduced to 20 mm.

8.1.2.2 Place the hook tape on a flat surface with the pile uppermost and then place the loop tape on top with the pile facing downwards so that only the selected length of overlap together with the overall width make a closure, using minimal hand pressure.

8.1.3 Traverse the roller device (5.2) at a rate of approximately 200 mm/s along the tapes in one direction, then immediately traverse in the opposite direction, then turn the mating tapes over.

NOTE The tapes are turned over to minimise curvature.

8.1.4 Repeat the procedure until the roller has traversed the mating tapes five times in each direction, i.e. a total of ten times, taking care that:

- the centre of gravity of the roller does not deviate from the centre line of the tapes during this operation;

the roller covers the entire width of the mating tapes.

8.1.5 Conduct the test for each closure as follows:

8.1.5.1 Set up the tensile testing machine (5.1) such that the jaws are 100 mm apart.

8.1.5.2 Mount the combined test specimen (see 8.1) into the jaws of the tensile testing machine (5.1) such that the free end of the loop tape is in the upper jaw and the free end of the hook tape is in the lower jaw, taking care to align the test specimen in order that the force applied is uniformly distributed across the width of the closure.

8.1.5.3 Set the tensile machine in motion at a constant rate of jaw separation of 100 mm/min \pm 10 mm/min. Record the maximum force against jaw separation, F_i , until either the closure has been separated or one of the tapes has undergone tensile failure. If failure occurs, record the mode of failure.

In the event that a tensile failure occurs, then the breaking force shall be considered as the force required to shear the closure.

8.2 Shear strength after repeated opening and closing

8.2.1 Measure the effective width of the fasteners by using the procedure in 8.1.1.